

Active sites characterisation using adsorption microcalorimetry at reaction temperature

S. Wrabetz¹, T.C.R. Rocha², D. Teschner¹, A. Knop-Gericke¹, G. Vilé³, J. Pérez-Ramírez³ and R. Schlögl¹

¹ Fritz-Haber-Institut der Max-Planck-Gesellschaft, 14195 Berlin, Germany, wrabetz@fhi-berlin.mpg.de

² Laboratório Nacional de Luz Síncrotron, Brazil ³ ETH Zurich, Switzerland

Heterogeneous catalysis involves specific chemical interactions between the surface of a solid and the reacting gas (or liquid phase) molecules. The catalytic cycle is generally composed of absorption/desorption steps, and surface reaction processes. The knowledge about heat of adsorption of reactant on the surface of a catalyst at reaction temperature ($T_{\text{react.}}$) can contribute to a better understanding of the complex microkinetics. Since perhaps only a minor fraction of all surface atoms form active centers, the determination of their number, strength and energy distribution requires a sensitive analytical method. We focus here on adsorption microcalorimetry at reaction temperature [1] and present two projects i) the dynamics of Ag-O system depending on time/temperature/pressure studied by oxygen adsorption at 150°C and 230°C ($T_{\text{react.}}$) and ii) 1-hexyne adsorption at 80°C ($T_{\text{react.}}$) on supported ceria, being unexpectedly active in the three-phase semi-hydrogenation of 1-hexyne.

i) Based on XPS, DFT calculations and microcalorimetry we have developed a picture to explain the Ag-O dynamics during thermal treatments and ethylene epoxidation. Essential processes are surface reconstruction, oxygen dissolution to subsurface and surface oxide growth at pressure between 10^{-1} and 1 mbar O_2 and at 230°C. These reaction steps are characterized by a saturation concentration of oxygen of $1.5 \mu\text{mol}_{O_2}/\text{g}_{Ag}$ and a differential heat of adsorption of $>50 - 120 \text{ kJmol}^{-1}$.

ii) In order to correlate the catalytic performance with characteristic properties of ceria, the chemisorption of 1-hexyne at $T_{\text{react.}}=80^\circ\text{C}$ and r.t. was studied on two differently active 20wt% $\text{CeO}_2/\text{TiO}_2$ catalysts. The 20wt% $\text{CeO}_2/\text{TiO}_2$ -WI catalyst (wet impregnation) shows a much higher alkyne conversion than the 20wt% $\text{CeO}_2/\text{TiO}_2$ -DI catalyst (dry impregnation). In both cases, the olefin selectivity is constant at 100%. Figure 1 shows that for both catalysts the differential heat of adsorption profile as a function of 1-hexyne uptake reveals a very strong adsorption at the initial stage (up to 900 kJmol^{-1}) suggesting multiple dehydrogenation steps taking place. After approximately 0.01 mmol g^{-1} , the heat of adsorption stabilizes around 200 kJmol^{-1} . This heat of adsorption resembles the energy released upon a single dehydrogenation step of acetylene.[2] Further adsorption takes place with slowly decreasing heat evolution up to 0.22 mmol g^{-1} for the more active 20wt% $\text{CeO}_2/\text{TiO}_2$ -WI and up to 0.16 mmol g^{-1} for the less active 20wt% $\text{CeO}_2/\text{TiO}_2$ -DI. The chemisorption process is irreversible (Figure 1). The regeneration of the catalyst surface using H_2 (at 150°C) has been somewhat more successful for the more active catalyst. The more active catalyst is characterized by a higher amount of adsorption places for 1-hexyne and a slightly easier regeneration of the surface after 1-hexyne contact at reaction temperature. Furthermore, the obtained results indicate that under reaction conditions a significant portion of the surface sites is covered by dehydrogenated species and is not available for hydrogenation. This is in line with DFT calculations of acetylene adsorption on $\text{CeO}_2(111)$ showing that the most preferred adsorption mode is dissociative with respect to the C-H bond.[2] Nevertheless, the remaining small number of surface sites are active and selective in alkyne hydrogenation.

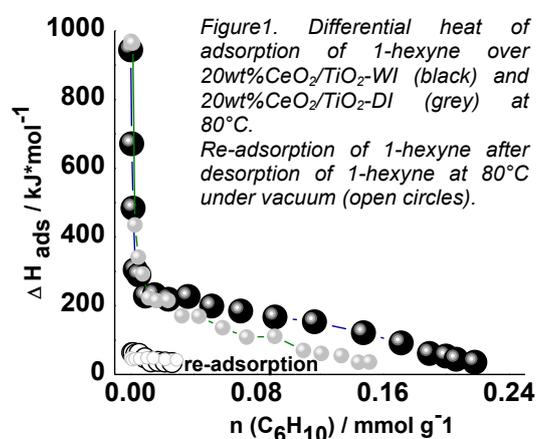


Figure 1. Differential heat of adsorption of 1-hexyne over 20wt% $\text{CeO}_2/\text{TiO}_2$ -WI (black) and 20wt% $\text{CeO}_2/\text{TiO}_2$ -DI (grey) at 80°C. Re-adsorption of 1-hexyne after desorption of 1-hexyne at 80°C under vacuum (open circles).

References:

- [1] (a) S. Wrabetz, R. Schlögl, F. Jentoft et al., *J. Catal.* 269 (2010) 351-358. (b) Amakawa, K., Wrabetz, S., Kröhnert, J., Tzolova-Müller, G., Schlögl, R., Trunschke, A.; *J. Am. Chem. Soc.*, 134 (28) (2012) 11462-11473. (c) B. Frank, S. Wrabetz, A. Trunschke, R. Schlögl, et al., *ChemPhysChem* 12 (2011) 2709-2713. (d) R. Arrigio, S. Wrabetz, R. Schlögl et al., *PCCP* 14 (2012) 10523-10532. (e) G. Vilé, S. Wrabetz, L. Floryan, M.E. Schuster, F. Girgsdies, D. Teschner, J. Pérez-Ramírez, *Chem. Cat. Chem.*, 2014 DOI: 10.1002/cctc.201402124.
- [2] J. Carrasco, G. Vilé, D. Fernández-Torre, R. Pérez, J. Pérez-Ramírez, M. V. Ganduglia-Pirovano, *J. Phys. Chem. C* 2014, 118, 5352.